

Mn and Fe impurities in MgB_2

P. Jiji Thomas Joseph and Prabhakar P. Singh

*Department of Physics, Indian Institute of Technology Bombay, Mumbai, India
400076*

Abstract

Based on first principles calculations, we show that Mn impurities are magnetic in MgB_2 due to exchange-splitting of d_{3z^2-1} band and they substantially modify B p_σ and p_π bands through hybridization. Thus, Mn impurities could act as strong magnetic scattering centers leading to pair-breaking effects in MgB_2 . In contrast, we find Fe impurities in MgB_2 to be nearly non-magnetic.

Key words: impurity, magnetic moment, local-density approximation

PACS: 71.20.-b, 71.20.Be, 74.25.Jb, 71.15.Nc

Magnetic impurities in a conventional phonon-mediated single band superconductor [1] induce pair-breaking effects via spin-flip scattering [2]. However, for an unconventional multi-band superconductor, pair-breaking seems to be most probable from inter-band scattering [3,4,5], and thus it is not expected to depend solely on the exact atomic nature of the impurity. Since the discovery of superconductivity in MgB_2 [6], now confirmed to be a two-band superconductor [7,8,9,10,11,12,13,14,15], previous studies of chemical substitutions have been largely confined to examining the effects of inter-band and intra-band scattering of the electrons. However, due to the orthogonality of B p_σ and p_π orbitals, the inter-band scattering effects which could lead to gap merging have not been observed in MgB_2 so far, although the superconducting transition temperature T_C showed a steady decrease as a function of increasing impurity concentration [5,16]. Of particular interests were Al [17,18,19,20,21] and $3d$ transition-metal substitutions [22,23,24,25,26,27,28,29] in the Mg sub-lattice and C substitutions [30,31,32,33,34] in the B sub-lattice of MgB_2 .

Of all impurity substitutions studied so far, Mn shows the most rapid decrease in T_C as a function of its increasing concentration in MgB_2 [22,23,25]. However, no evidence of inter-band scattering was observed, instead the role

Email address: ppsingh@phy.iitb.ac.in (P. Jiji Thomas Joseph and Prabhakar P. Singh).

of magnetic exchange splitting of the bands in Mn -substituted MgB_2 was emphasized [23]. Earlier, it was shown that the inter-band scattering would be important if the lattice was distorted locally around the impurities [35]. In this regard, substituting C impurities for B atoms would have only a weak effect on inter-band scattering because it does not change the local symmetry. In contrast, substitutions in the Mg plane could create out-of-plane distortions and change the local point symmetry of nearby B atoms, resulting in a mixing of the in-plane $p_{x(y)}$ orbitals and the out-of-plane p_z orbital. Under these circumstances significant σ - π scattering would occur.

In this letter, we show that Mn impurities are magnetic in MgB_2 due to exchange-splitting of d_{3z^2-1} band and they substantially modify B p_σ and p_π bands through hybridization. In contrast, we find Fe impurities in MgB_2 to be nearly non-magnetic. Thus, the Mn impurities could act as strong magnetic scattering centers leading to pair-breaking effects in MgB_2 . This may explain the rapid decrease of T_c in $Mg_{1-x}Mn_xB_2$ with increasing x , while in $Mg_{1-x}Fe_xB_2$ a relatively slow decrease in T_c with x may only be due to disorder-induced scattering of the electrons. Before we discuss our results in detail, we briefly describe the computational details.

The normal metal electronic structure of the disordered alloys $Mg_{1-x}Mn_xB_2$ and $Mg_{1-x}Fe_xB_2$ are calculated using the Korringa-Kohn-Rostoker (KKR) Green's function method formulated in the atomic sphere approximation (ASA) [36], which has been corrected by the use of both the muffin-tin correction for the Madelung energy, needed for obtaining an accurate description of ground state properties in the ASA [37], and the multipole moment correction to the Madelung potential and energy which significantly improves the accuracy by taking into consideration the non-spherical part of polarization effects [38,39]. Chemical disorder was taken into account by means of coherent-potential approximation (CPA) [40]. The exchange and correlation were included within the local density approximation (LDA) using the Perdew-Wang parameterization [41] of the many-body calculations of Ceperley and Alder [42]. During the self-consistent procedure the reciprocal space integrals were calculated by means of 1771 $\mathbf{k}$ -points in the irreducible part of the hexagonal Brillouin zone (BZ), while the energy integrals were evaluated on a semicircular contour in the complex energy plane using 20 energy points distributed in such a way that the sampling near the Fermi energy was increased. When calculating the density of states the number of $\mathbf{k}$ -points were increased to 2299. The Green's function was evaluated for 1000 points on a line in the complex energy plane parallel to the real axis and was then analytically continued towards the real axis. The atomic sphere radii of Mg and B were kept as 1.294 and 0.747, respectively of the Wigner-Seitz radius. The sphere radii of the $3d$ substituents were kept the same as that of Mg itself. The overlap volume resulting from the blow up of the muffin-tin spheres was approximately 10%, which is reasonable within the accuracy of the approximation [43]. The charge self-consistency it-

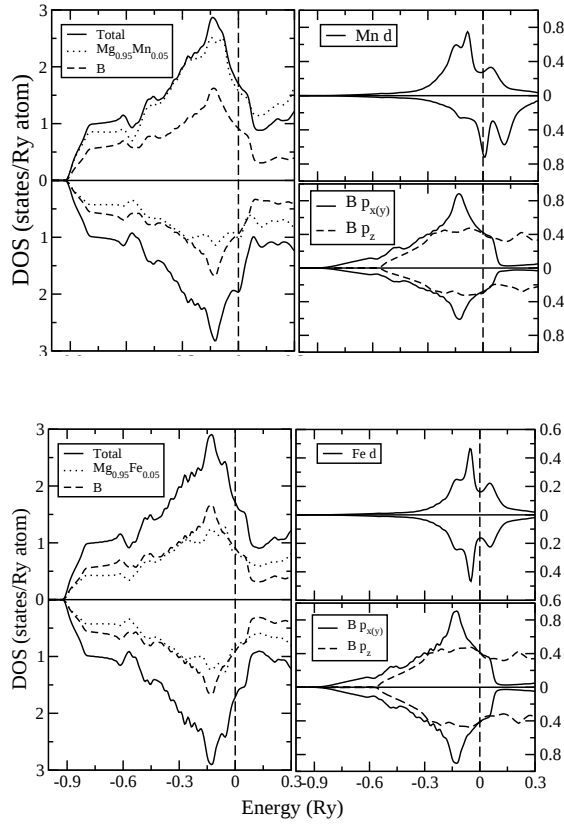


Figure 1. The spin polarized, total and sub-lattice resolved partial densities of states of $Mg_{0.95}Mn_{0.05}B_2$ (top panel) and $Mg_{0.95}Fe_{0.05}B_2$ (bottom panel) alloys calculated as described in the text. The transition-metal d and B p densities of states for the respective alloys are also shown in the side panels. The dashed vertical line through energy zero represents the Fermi energy.

erations were accelerated using the Broyden's mixing scheme [44], the CPA self consistency was speeded up using the prescription of Abrikosov *et al* [45]. The calculations for $Mg_{1-x}Mn_xB_2$ and $Mg_{1-x}Fe_xB_2$ alloys with $x = 0.05$ were carried out at the experimental lattice parameters of MgB_2 [6], assuming a rigid underlying lattice. The effects of local lattice relaxation as well as any possible short-range ordering effects are not considered. Our results for $Mg_{1-x}Mn_xB_2$ and $Mg_{1-x}Fe_xB_2$ for $x = 0.05$ are analyzed in terms of total, sub-lattice resolved partial densities of states, and Bloch spectral density $A_B(E, \mathbf{k})$ [46] evaluated at high symmetry points of the hexagonal BZ. The electronic structure of body-centered cubic (bcc) Fe is calculated with a similar setup using the experimental lattice constant $a = 5.425$ a.u.. The density of states of bcc Fe is calculated with 2470 $\mathbf{k}$ -points in the irreducible BZ.

The calculated density of states (DOS) at the Fermi energy, E_F , of MgB_2 was determined to be 3.493 states/Ry atom, which is consistent with previous reports [47,48]. For $Mg_{0.95}Mn_{0.05}B_2$ and $Mg_{0.95}Fe_{0.05}B_2$ alloys, the spin polarized calculations showed a lower total energy when compared to the spin unpolarized calculations, suggesting the role of exchange splitting of the

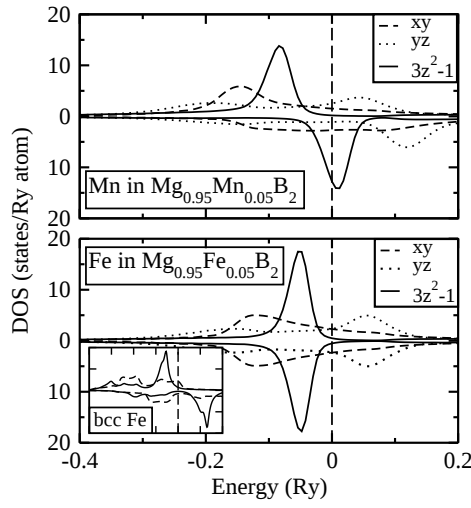


Figure 2. The spin polarized, transition-metal d -projected DOS in $Mg_{0.95}Mn_{0.05}B_2$ (top panel) and $Mg_{0.95}Fe_{0.05}B_2$ (bottom panel) alloys, resolved into three non-degenerate xy ($x^2 - y^2$), yz (zx), and $3z^2 - 1$ symmetry components. The inset in the bottom panel shows the spin polarized, d -projected DOS of bcc Fe , resolved into two non-degenerate xy (yz, zx) (dashed line) and $3z^2 - 1$ ($x^2 - y^2$) (solid line) symmetry components. In the inset figure, the x -axis corresponds to energy ranging from -0.4 Ry to 0.2 Ry, while the y -axis represents the DOS from 0 to 12 state/Ry/atom for both spins. The dashed vertical line through energy zero represents the Fermi energy. Note that the DOS in the figure corresponds to per transition-metal atom.

states, in particular for Mn substituted MgB_2 . The magnetic energies for $Mg_{0.95}Mn_{0.05}B_2$ and $Mg_{0.95}Fe_{0.05}B_2$ alloys are calculated to be 5.319 mRy and 0.001 mRy, respectively. The corresponding local magnetic moment for Mn is equal to $1.84 \mu_B/\text{atom}$, while Fe tends to be feebly magnetic with a local magnetic moment of $0.04 \mu_B/\text{atom}$. In Fig. 1 we show the spin polarized, total and sub-lattice resolved partial densities of states of $Mg_{0.95}Mn_{0.05}B_2$ and $Mg_{0.95}Fe_{0.05}B_2$ alloys. In the same figure we also show the transition-metal d and B $p_{x(y)}$ and p_z DOS in these alloys. It is clear from Fig. 1 that the exchange-split Mn d orbitals in $Mg_{0.95}Mn_{0.05}B_2$ alloys make Mn impurities magnetic in MgB_2 . We also find a substantial distortion in the majority and minority B $p_{x(y)}$ and p_z bands due to their hybridization with the Mn d orbitals. In addition, we find the B p band to have a very small exchange-splitting of 0.7 mRy in $Mg_{0.95}Mn_{0.05}B_2$ but no splitting in $Mg_{0.95}Fe_{0.05}B_2$.

To gain further insight into such a contrasting behavior of Mn and Fe impurities in MgB_2 , we show in Fig. 2 the transition-metal d -projected DOS in $Mg_{0.95}Mn_{0.05}B_2$ and $Mg_{0.95}Fe_{0.05}B_2$ alloys, resolved into three non-degenerate xy ($x^2 - y^2$), yz (zx), and $3z^2 - 1$ symmetry components. We find that the band with $3z^2 - 1$ symmetry is the narrowest of all the d bands. Thus, a half-filled $3z^2 - 1$ band is more likely to induce exchange splitting than the other bands. In the case of Mn the minority $3z^2 - 1$ band is nearly half-filled,

resulting in an exchange-split d band. Our calculations show that the centers of the $d \uparrow$ and the $d \downarrow$ bands are separated by 0.114 Ry leading to the Stoner exchange integral I ($= \frac{d\uparrow - d\downarrow}{m}$) to be 0.062 Ry/ μ_B . However, in the case of Fe the additional one electron fills up the minority $3z^2 - 1$ band, as can be seen from Fig. 2, thereby making Fe nearly non-magnetic in MgB_2 . In addition, following the prescription of Liechtenstein *et al* [49], we have calculated the on-site Heisenberg exchange interaction J_0 . The values of J_0 for Mn and Fe alloys are found to be 0.7292 mRy and 0.0001 mRy respectively, confirming Mn to be magnetic and Fe to be nearly non-magnetic in MgB_2 .

It is instructive to compare the DOS of Fe in $Mg_{0.95}Fe_{0.05}B_2$ with that of bcc Fe as shown in the inset of Fig. 2, where the d -projected DOS of bcc Fe has been resolved into two non-degenerate xy (yz, zx) and $3z^2 - 1$ ($x^2 - y^2$) symmetry components. The calculated magnetic moment of bcc Fe is found to be 2.24 μ_B /atom. The most significant changes in the DOS of Fe involve $x^2 - y^2$ and $3z^2 - 1$ symmetry components. Due to the change in local symmetry, as one goes from bcc Fe to hexagonal $Mg_{0.95}Fe_{0.05}B_2$, the narrow $x^2 - y^2$ band of bcc Fe hybridizes with the $B p_{x(y)}$ bands of $Mg_{0.95}Fe_{0.05}B_2$ and gets broadened as shown in Fig. 2. The effects of hybridization on the $B p_{x(y)}$ DOS can be seen in Fig. 1 in the form of a hump around 0.14 Ry below the Fermi energy. On the other hand, the filling up of the minority $3z^2 - 1$ band by the extra electron results in an inward movement of the band by 0.15 Ry, making magnetism unsustainable in $Mg_{0.95}Fe_{0.05}B_2$.

Many of the superconducting properties of MgB_2 can be directly related to its normal state electronic structure. In particular, an understanding of how the additions of Mn and Fe impurities affect the electronic states over the entire BZ can be very useful in this regard. In Fig. 3 we show the spin polarized, $\mathbf{k}$ -resolved Bloch spectral density $A_B(E, \mathbf{k})$ for $Mg_{0.95}Mn_{0.05}B_2$ and $Mg_{0.95}Fe_{0.05}B_2$ alloys at Γ , A , M , H , K , and L points of the hexagonal BZ. As expected, the differences between majority and minority $A_B(E, \mathbf{k})$ are much more for $Mg_{0.95}Mn_{0.05}B_2$ alloys than for $Mg_{0.95}Fe_{0.05}B_2$ alloys over the entire BZ. New states, predominantly d in character are seen to form just below E_F at Γ and K points. The disorder-induced broadening of the doubly degenerate $B p_\sigma$ states located between $-0.05 < E < +0.05$ at Γ and $B p_\pi$ states just above E_F at M point can be seen clearly. At M point, the lowest lying peak is characteristic of the s band, while the next two peaks correspond to the p_σ bands. We find that the p_σ bands at M point in ordered MgB_2 are relatively far apart in comparison to the Mn and Fe substituted systems. A change in the dispersion of bands is expected to affect the three dimensionality of the Fermi surface [47] of the substituted materials (a detailed comparison will be published elsewhere). We also note that in transition-metal diborides, such as TaB_2 and others, a strong metal d hybridization with the $B p$ bands is observed in A - L - H plane of the BZ [50,51]. However, in the case of Mn and Fe impurities, the d bands are narrower and only the states that are close to

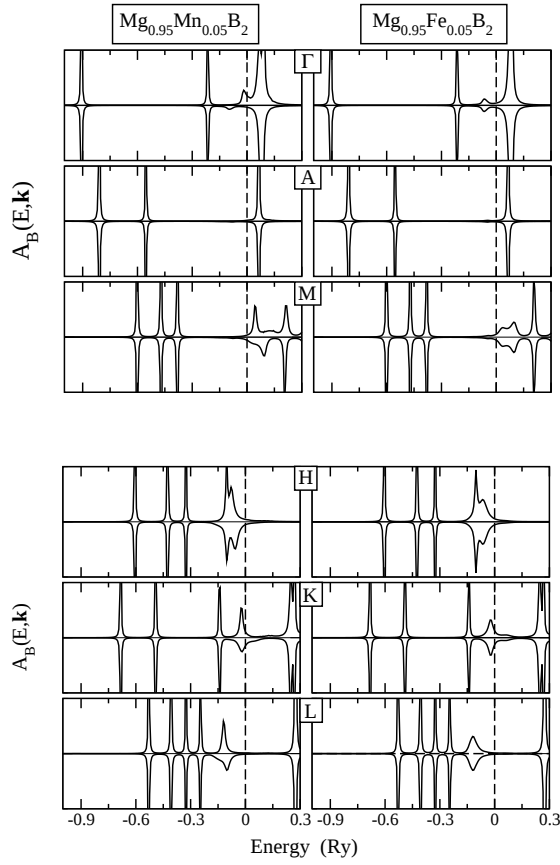


Figure 3. The spin polarized, $\mathbf{k}$ -resolved Bloch spectral density $A_B(E, \mathbf{k})$ for $Mg_{0.95}Mn_{0.05}B_2$ (left) and $Mg_{0.95}Fe_{0.05}B_2$ (right) alloys at Γ , A and M (top panel), and H , K , and L points of the hexagonal Brillouin zone. The dashed vertical line through energy zero represents the Fermi energy.

E_F are affected.

In summary, we have carried out density-functional-based electronic structure calculations to study the effects of Mn and Fe substitutions on the σ and π bands of MgB_2 . The self-consistent calculations for $Mg_{0.95}Mn_{0.05}B_2$ and $Mg_{0.95}Fe_{0.05}B_2$ alloys show that Mn forms a local magnetic moment of $1.84 \mu_B/\text{atom}$ while Fe tends to remain feebly magnetic with a local magnetic moment of $0.04 \mu_B/\text{atom}$. Further, the $\mathbf{k}$ -resolved Bloch spectral density of states at Γ , A , M , H , K , and L points of the hexagonal Brillouin zone show that for Mn substituted alloys the σ bands of MgB_2 are strongly hybridized with the Mn d bands and undergo considerable spin-dependent modifications when compared to its Fe counterparts. Given that p_σ and p_π orbitals are responsible for superconductivity in MgB_2 , Mn impurities could, therefore, act as strong magnetic scattering centers leading to pair-breaking effects. In contrast, the Fe impurities in MgB_2 are nearly non-magnetic with essentially no pair-breaking effects.

One of us (PJTJ) would like to thank Dr. Andrei Ruban for providing the

KKR-ASA code. Discussions with Dr. Igor Mazin on the electronic structure properties of MgB_2 is gratefully acknowledged.

References

- [1] J. Bardeen, L. N. Cooper, and J. R. Schrieffer, Phys. Rev. 108, 1175 (1957)
- [2] A. A. Abrikosov, L. P. Gor'kov, and I. Ye. Dzyaloshinskii, Methods of Quantum Field Theory in Statistical Physics, Dover Publications, New York, (1975)
- [3] A. Gurevich, Phys. Rev. B 67, 184515 (2003)
- [4] A. A. Golubov and I. I. Mazin, Phys. Rev. B 55, 015146 (1997)
- [5] I. I. Mazin, O. K. Andersen, O. Jepsen, O. V. Dolgov, J. Kortus, A. A. Golubov, A. B. Kuzmenko, and D. van der Marel, Phys. Rev. Lett. 89, 107002 (2002)
- [6] J. Nagamatsu, N. Nakagawa, T. Muranaka, Y. Zenitani, and J. Akimitsu, Nature 410, 63 (2001)
- [7] G. Karapetrov, M. Iavarone, W. K. Kwock, G. W. Crabtree, and D. G. Hinks, Phys. Rev. Lett. 86, 4374 (2001)
- [8] M.R. Eskildsen, M. Kugler, S. Tanaka, J. Jun, S.M. Kazakov, J. Karpinski, and O. Fisher, Phys. Rev. Lett. 89, 187003 (2002)
- [9] H. Schmidt, J.E. Zasadzinski, K.E. Gray, and D.G. Hinks, Phys. Rev. Lett. 88, 127002 (2002)
- [10] X.K. Chen, M.J. Kostantinovic, J.C. Irwin, D.D. Lawrie, and J.P. Franck, Phys. Rev. Lett. 87, 157002 (2001)
- [11] F. Bouquet, R.A. Fisher, N.E. Phillips, D.G. Hinks, and J.D. Jorgensen, Phys. Rev. Lett. 87, 047001 (2001)
- [12] J. J. Tu, G. L. Carr, V. Perebeinos, C. C. Homes, M. Strongin, P. B. Allen, W. N. Kang, E. -M. Choi, H. -J. Kim, and S. -I. Lee, Phys. Rev. Lett. 87, 277001 (2001)
- [13] M.-S. Kim, J.A. Skinta, T.R. Lem-berger, W.N. Kang, H.-J. Kim, E.-M. Choi, and S.-I. Lee, Phys. Rev. B 66, 064511 (2002)
- [14] A.B. Kuzmenko, E. P. Mena, H. J. A. Molegraaf, D. van der Marel, B. Gorshunov, M. Dressel, I. I. Mazin, J. Kortus, O. V. Dolgov, T. Muranaka, and J. Akimitsu, Solid State Commun. 121, 479 (2002)
- [15] S. Souma, Y. Machida, T. Sato, T. Takahashi, H. Matsui, S-C. Wang, H. Ding, A. Kaminski, J. C. Campuzano, S. Sasaki, and K. Kadowaki, Nature 423, 65 (2003)
- [16] A. Y. Liu, I. I. Mazin, and J. Kortus, Phys. Rev. Lett. 87, 087005 (2001)

- [17] J. S. Slusky, N. Rogado, K. A. Regan, M. A. Hayward, P. Khalifah, T. He, K. Inumaru, S. M. Loureiro, M. K. Haas, H. W. Zandbergen, R. J. Cava, *Nature* 410, 343 (2001)
- [18] P. Postorino A. Congeduti, P. Dore, A. Nucara, A. Bianconi, D. Di Castro, S. De Negri, and A. Saccone, *Phys. Rev. B* 65, 020507 (2001)
- [19] M. Putti, M. Affronte, P. Manfrinetti, and A. Palenzona, *Phys. Rev. B* 68, 094514 (2003)
- [20] J. Karpinski, N. D. Zhigadlo, G. Schuck, S. M. Kazakov, B. Batlogg, K. Rogacki, R. Puzniak, J. Jun, E. Muller, P. A. Wagli, R. Gonnelli, D. Daghero, G. A. Ummarino, and V. a A. Stepanov, *Phys. Rev. B* 71, 174506 (2005)
- [21] A. J. Zambano, A. R. Moodenbaugh, and L. D. Cooley, cond-mat/0507041 (2005)
- [22] Sheng Xu, Yutaka Moritomo, Kenichi Kato, Arao Nakamura, cond-mat/0104534
- [23] K. Rogacki, B. Batlogg, J. Karpinski, N.D. Zhigadlo, G. Schuck, S.M. Kazakov, P. Wagli, R. Puzniak, A. Wisniewski, F. Carbone, A. Brinkman, and D. van der Marel, cond-mat/0510227
- [24] P. P Singh and P . J. T. Joseph, *J. Phys. Condens. Matter* 14, 12441, (2002)
- [25] S. Xu, Y. Moritomo, K. Kato, and A. Nakamura, *J. Phys. Soc. Japan* 70, 1889 (2001)
- [26] Y. D. Gao, J. Ding, G. V. S. Rao and B. V. R. Chowdari, *J. Appl. Phys.* 93, 8656 (2003)
- [27] M. Kuhberger and G. Gritzner, *Physica C* 370, 39 (2002)
- [28] S. X. Dou, S. Soltanian, Y. Zhao, E. Getin, Z. Chen, O. Shcherbakova, and J. Horvat, *Supercond. Sci. Technol.* 18, 710 (2005)
- [29] H. Zhang, J. Zhao, and L. Shi, *Physica C* 424, 79 (2005)
- [30] S. M. Kazakov, R. Puzniak, K. Rogacki, A. V. Mironov, N. D. Zhigadlo, J. Jun, Ch. Soltmann, B. Batlogg, and J. Karpinski, *Phys. Rev. B* 71, 024533 (2005)
- [31] D. Daghero , R.S. Gonnelli, A. Calzolari, G. A. Ummarino, Valeria Dellarocca, V. A. Stepanov, N. Zhigadlo, S. M. Kazakov, J. Karpinski, *physica status solidi* 2, 1656 (2005)
- [32] S. Lee, T. Masui, A. Yamamoto, H. Uchiyama, and S. Tajima, *Physica C* 397, 7 (2003). T. Masui, S. Lee, and S. Tajima, *Phys. Rev. B* 70, 024504 (2004)
- [33] A. Bharathi, S. J. Balaselvi, S. Kalavathi, G. L. N. Reddy, V. S. Sastry, Y. Hariharan, and T. S. Radhakrishnan, *Physica C* 370, 211 (2002)
- [34] G. A. Ummarino, D. Daghero, R. S. Gonnelli and A. H. Moudden, *Phys. Rev. B* 71, 134511 (2005)
- [35] Steven C. Erwin and I. I. Mazin, *Phys. Rev. B* 68, 132505 (2003)

- [36] I. Turek, V. Drchal, J. Kudrnovsky, M. Sob, P. Weinberger, Electronic structure of disordered alloys, surfaces and interfaces, Kluwer Academic Publishers, Boston (1997)
- [37] N. E. Christensen and S. Satpathy, Phys. Rev. Lett. 55, 600 (1985)
- [38] A. V. Ruban and H. L. Skriver, Computational Materials Science, 15, 119 (1999)
- [39] P. A. Korzhavyi, A. V. Ruban, I. A. Abrikosov, and H. L. Skriver, Phys. Rev. B 51, 5773 (1995)
- [40] P. Soven Phys. Rev. 156, 809 (1967)
- [41] J. P. Perdew and Y. Wang, Phys. Rev. B 45, 13244 (1992)
- [42] D. M. Ceperley and B. J. Alder, Phys. Rev. Lett. 45, 566 (1980)
- [43] H. L. Skriver, The LMTO method, Muffin tin orbitals and electronic structure, Springer-Verlag (1984)
- [44] D. D. Johnson, Phys. Rev. B 38, 12807-12813 (1988)
- [45] I. A. Abrikosov, S. I. Simak, B. Johansson, A. V. Ruban, and H. L. Skriver, Phys. Rev. B 56, 9319 (1997)
- [46] J. S. Faulkner and G. M. Stocks, Phys. Rev. B 21, 3222 (1980)
- [47] J. Kortus, I. I. Mazin, K. D. Belashchenko, V. P. Antropov, and L. L. Boyer, Phys. Rev. Lett. 86, 4656 (2001)
- [48] P. P. Singh, Phys. Rev. Lett. 87, 087004 (2001)
- [49] A. I. Liechtenstein, M. I. Katsnelson, V. P. Antropov and V. A. Gubanov, J. Magn. Magn. Mater. 67, 65 (1987)
- [50] J. Nakamura, N. Yamada, K. Kuroki, T. A. Callcott, D. L. Ederer, J. D. Denlinger, and R. C. C. Perera, Phys. Rev. B 64, 174504 (2001)
- [51] H. Rosner, W. E. Pickett, S.-L. Drechsler, A. Handstein, G. Behr, G. Fuchs, K. Nenkov, K.-H. Muller, and H. Eschrig, Phys. Rev. B 64, 144516 (2001)